


Faraday Discussions

Accepted Manuscript



This is an Accepted Manuscript, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this Accepted Manuscript with the edited and formatted Advance Article as soon as it is available.

You can find more information about Accepted Manuscripts in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this Accepted Manuscript or any consequences arising from the use of any information it contains.

This article can be cited before page numbers have been issued, to do this please use: K. Yoo, G. S. Lee, H. W. Lee, B. Kim and J. G. Kim, *Faraday Discuss.*, 2022, DOI: 10.1039/D2FD00080F.

ARTICLE

Mechanochemical Solid-State Vinyl Polymerization with Anionic Initiator

Kwangho Yoo^{a,b,†}, Gue Seon Lee^{a,†}, Hyo Won Lee^{a,†}, Byeong-Su Kim^b, and Jeung Gon Kim^{*,a}Received 00th January 20xx,
Accepted 00th January 20xx

DOI: 10.1039/x0xx00000x

Mechanochemistry has been extended to various polymer syntheses to achieve efficiency, greenness, and new products. However, many fundamental polymerization reactions have not been explored, although anionic polymerization of vinyl compounds has been pursued under mechanochemical conditions. Two solid monomers, 4-biphenyl methacrylate and 4-vinyl biphenyl, each representing methacrylate and styrenic classes, respectively, were reacted with secondary butyl lithium under high-speed ball-milling. The alkyl-anion-promoted polymerization process was established by excluding radical initiation and producing the expected polymers with good efficiency. However, the generally expected features of anionic polymerization, such as molecular weight control and narrow dispersity, were not observed. Analysis of the milling parameters, reaction monitoring, and microstructural analysis revealed that the mechanism of the mechanochemical process differs from that of conventional anionic polymerizations. The mechanical force fractured the newly formed polymer chains via anionic initiation and generated macroradicals, which participated in the polymerization process. The anionic process governs the initiation step and the radical process becomes dominant during the propagation step.

Introduction

Mechanochemistry has become a significant choice in synthetic chemistry. Mechanical motions such as collision and friction in ball-milling or shearing in twin-screws allow direct mixing of reagents and supply energy. Reducing or eliminating the solvent in the mechanochemical process results in cleaner, faster, and more straightforward synthesis than in conventional systems.^[1] Mechanochemistry also provides a resolution to the issue of differences in the solubility of the reagents or the decomposition of intermediates in solution.^[2] This process can also produce new compounds that are inaccessible in solution. Almost all areas of synthetic chemistry have examples that demonstrate the virtue of mechanochemistry.^[3]

These advantages have also affected the polymer synthesis community. Historically, the mechanochemistry of polymers has meant the involvement of chain degradation, molecular weight reduction, and mechanical deterioration.^[4] The construction of macromolecular structures from small molecules using mechanical forces has evolved.^[5] Since Kargin's pioneering works on the polymerization of styrenic and acrylic monomers in the 1950s, there have been some sporadic reports that mostly focused on radical polymerization.^[6] In the 21st century, which is the era of green chemistry, attention to mechanochemical polymer synthesis has increased. Various polymerization techniques are now on the list of mechanochemistry, such as radical polymerization of vinyl compounds,^[6] ring-opening polymerization of cyclic esters and carbonates,^[7] metathesis polymerization,^[8] and step polymerization to generate polyaniline, polyphenylene, poly(phenylene vinylene), and polyurethane.^[9] These examples demonstrate that mechanochemical polymer synthesis offers many merits such as a) advancing green metrics in polymer science, b) improving the efficiency of syntheses, c) better performance of the resulting polymers, and d) polymerization of monomers or producing polymers with limited solubility.

However, many polymerization methods, including anionic polymerization, have not been validated under mechanochemical conditions. Fast initiation and propagation by highly nucleophilic anions produce many polymeric materials in the course of daily life.^[10] The high level of precision is another merit of anionic polymerization. However, reactions involving highly reactive alkyl anions require low-temperature conditions and careful handling of reagents to achieve the expected goals, which retard investigations of these reactions under other conditions.^[11] With an interest in expanding the scope of mechanochemical chain polymerization,^[7] our research group has commenced studies on solid-state mechanochemical polymerization of an anionic

^a Department of Chemistry and Research Institute of Physics and Chemistry, Jeonbuk National University, Jeonju 54896, Republic of Korea
E-mail: jeunggonkim@jbnu.ac.kr

^b Department of Chemistry, Yonsei University, Seoul 03722, Republic of Korea

† These authors contributed equally


Electronic Supplementary Information (ESI) available: [details of any supplementary information available should be included here]. See DOI: 10.1039/x0xx00000x

initiator and vinyl monomers and found distinctive characteristics compared to the solution systems. Anionic initiators promote the initiation step, but propagation is a radical process. The details of our study and its findings are presented herein (Figure 1).

[View Article Online](#)


DOI: 10.1039/D2FD00080F

Radical Polymerizations




Kargin (1959)
Oprea (1980s)
Kuzuya (1990s)
Bielawski (Controlled, 2020)

Ring-Opening Polymerizations

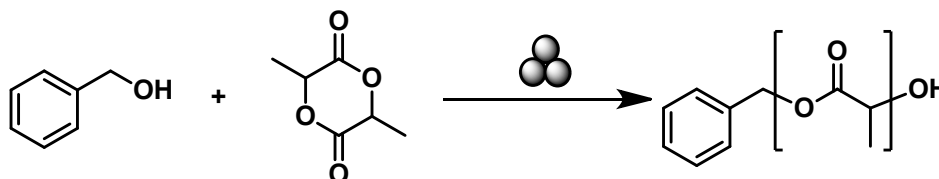

Kim (2017)
Giani (2021)

Anion-initiated Polymerizations

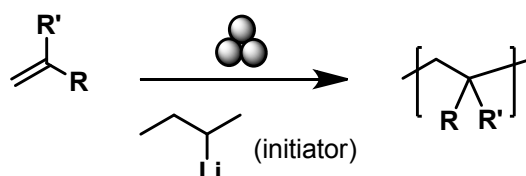

This work

**Anionic initiation
Radical propagation**

Figure 1. Brief summary of mechanochemical chain polymerizations.

Results and discussion

View Article Online

DOI: 10.1039/D2FD00080F


Ball-milling Anionic Polymerizations: Avoiding Radical Initiation

Polymerization of vinyl monomers, such as styrene and (meth)acrylate, constitutes the largest portion of polymer production. Mechanochemists have also paid attention to vinyl polymerization, anticipating a fast rate and green chemistry. An initial trial by Kagan et al. revealed that grinding monomers by ball-milling promotes polymerization.^[6a-d] Later studies by Oprea and Kuzuya realised that ball-milling vinyl polymerization is a radical process and does not require a radical initiator.^[6e-i] They proposed a free radical polymerization mechanism involving electron release and transfer from the milling materials upon high-energy collisions.^[6e,h] However, self-initiation of the monomers may also be possible.^[5,12]

When ionic polymerization is performed in a mechanochemical ball-milling system, a competing radical process should not occur. Thus, we employed low-energy ball-milling conditions under which radical initiation does not occur. Under these conditions, only highly reactive anionic species would trigger polymerization (Table 1). Two solid monomers, 4-vinyl biphenyl (4-VBP) and 4-biphenyl methacrylate (4-BPMA), were polymerized, representing the styrenic and methacrylate species, respectively. Each vinyl compound was milled with various balls at various vibration frequencies. Many ball-milling studies have employed stainless steel containers and balls because of their high density (high energy) and economy.^[5] However, metallic stainless steels can easily release electrons and facilitate radical generation. Therefore, herein, ceramic zirconia jars and balls of lower density were employed, with the expectation of less radical-initiated polymerization. 4-VBP or 4-BPMA (100 mg) was added to a 10 mL zirconia milling jar with two zirconia balls with diameters of 8 mm under inert conditions. The vessel was assembled and placed in a vibratory ball-mill (Retsch MM400). After an hour at a frequency of 30 Hz, proton nuclear magnetic resonance (¹H NMR) spectroscopy analysis with CH₂Br₂ as an internal standard revealed quantitative polymer formation: 99% for 4-VBP and 95% for 4-BPMA (entry 1). To mitigate undesirable radical processes, the energy was further reduced. At a vibrational frequency of 20 Hz, radical polymerization was significantly retarded (entry 2). Only 27% of 4-VBP participated in the polymerization, whereas 4-BPMA remained unreacted.

The effect of the ball size was further evaluated, as this parameter exerted a profound effect in our previous studies on the ring-opening polymerization of lactides.^[7a] At 20 Hz, 4-BPMA remained unreacted regardless of the ball size, but 4-VBP conversion was sensitive to the scale of impact (entries 3 and 4). With a single 10 mm ball, 71% of 4-VBP was converted to the corresponding polymer. With 5 mm balls (8 ea), there was no conversion to the polymer. Because the 5 mm balls did not initiate the polymerization of either 4-VBP or 4-BPMA at 20, 25, and 30 Hz (entries 4–6), the anion-initiated polymerization was evaluated with 5 mm balls in the ensuing reactions.

Table 1. Mechanochemical radical polymerization of 4-VBP and 4-BPMA without an external initiator^[a]

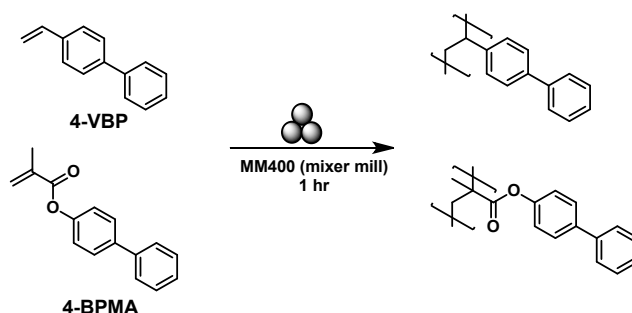

Entry	Container	Balls	Hz	Conv. (%) ^[b]	
				4-VBP	4-BPMA
1	Zirconia (10 mL)	Zirconia, 8 mm, 2 ea	30	99	95
2	Zirconia (10 mL)	Zirconia, 8 mm, 2 ea	20	27	< 1
3	Zirconia (10 mL)	Zirconia, 10 mm, 1 ea	20	71	< 1
4	Zirconia (10 mL)	Zirconia, 5 mm, 8 ea	20	<1	< 1
5	Zirconia (10 mL)	Zirconia, 5 mm, 8 ea	25	<1	< 1
6	Zirconia (10 mL)	Zirconia, 5 mm, 8 ea	30	<1	< 1


^[a]Average values from two experiments. ^[b]Determined by ¹H NMR spectroscopy with CH₂Br₂ as an internal standard

Alkyl Lithium-initiated Polymerization – Anionic initiation and radical propagation[View Article Online](#)

To evaluate the mechanochemical anionic polymerization, a widely used initiator, secondary butyl lithium (*s*-BuLi) was applied to solid 4-VBP or 4-BPMA (Table 2). Commercial *s*-BuLi (1.4 M solution in cyclohexane) was used. The use of solid *s*-BuLi was initially attempted, but the poor reproducibility of the reaction prompted us to use this solution. The monomer and *s*-BuLi were added to a 10 mL zirconia jar with eight zirconia balls of 8 mm diameter. All polymerizations were assembled under inert atmosphere in a dry box and moved to a mixer mill (MM400) at 30 °C.

First, the monomer to initiator ratio ($[M]/[I]$) was examined for $[M]/[I] = 25, 50, \text{ and } 100$ (entries 1–6). All reactions produced the corresponding polymers. Because this condition does not promote radical initiation, the products are from anionic initiation. A lower initiator loading resulted in less conversion, proving the direct involvement of *s*-BuLi in the initiation step. However, molecular weight analysis by size exclusion chromatography (SEC) indicated that mechanochemical anionic polymerization may not be living polymerization. Well-controlled anionic polymerization is expected to afford precise control of the product size and distribution, where 1) the monomer consumption is linearly related to the initiator and molecular weight (or polymer chain length) and 2) the product exhibits narrow dispersity (\bar{D}).^[10,13] However, the mechanochemical reaction did not follow this trend. The expected degree of polymerization (DP_{exp}), which is the amount of reacted monomer per initiator, was poorly correlated with the number-average molecular weight (M_n) (Figure 2). In the case of 4-VBP, as DP_{exp} moved from 25, to 42 to 54, the M_n increased exponentially from 12.6 kg/mol to 40.7 kg/mol to 105 kg/mol, respectively (entries 1–3). For 4-BPMA, a 76% increase in DP_{exp} from 25 to 44 resulted in marginal chain extension (M_n moved from 42.0 kg/mol to 45.3 kg/mol (entries 5 and 6)). In addition, all polymerizations exhibited large dispersity. These results suggest that the kinetics established for living anionic polymerization are not valid under solid-state ball-milling conditions.

The effect of the vibrational frequency was investigated (entries 7–12). Higher frequencies resulted in higher conversions of both 4-VBP and 4-BPMA owing to better mixing and higher energy input. Poor reproducibility was observed in the case of 4-VBP at 20 Hz (entry 9). Two polymerizations were conducted simultaneously and produced a large discrepancy in M_n (40.7 kg/mol and 135 kg/mol), respectively. In general, 4-BPMA showed lower reactivity than 4-VBP, and low-energy conditions did not promote measurable conversions to the polymers (entries 11 and 12).

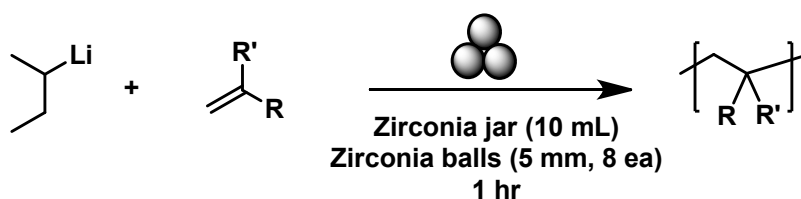Table 2. Polymerization of 4-vinyl biphenyl with *s*-BuLi initiator^[a,b]View Article Online
DOI: 10.1039/D2FD00080F


Entry	Monomer	Hz	[M]/[I]	Conv. (%) ^[c]	DP _{exp} ^[d]	M _n (kg/mol) ^[e]	Đ ^[e]
[M]/[I] variation set							
1	4-VBP	30	25	99	25	12.6	1.92
2		30	50	83	42	40.7	2.43
3		30	100	54	54	105	2.56

4	4-BPMA	30	25	73	18	35.6	1.75
5		30	50	50	25	42.2	1.81
6		30	100	44	44	45.3	1.88

Vibration energy variation set							
7	4-VBP	30	50	83	42	40.7	2.43
8		25	50	54	27	44.9	2.60
9		20	50	18	9	47.0/135	4.46/2.29

10	4-BPMA	30	50	50	25	42.2	1.81
11		25	50	<5	-	-	-
12		20	50	<1	-	-	-

^[a]Average values from two experiments. ^[b]*s*-BuLi solution (1.4 M in cyclohexane) was used. ^[c]Determined by ¹H NMR spectroscopy with CH₂Br₂ as an internal standard. ^[d]DP_{exp}=[M]/[I] X conversion. ^[e]Determined by SEC calibrated with polystyrene standards in tetrahydrofuran (THF) at 40 °C.

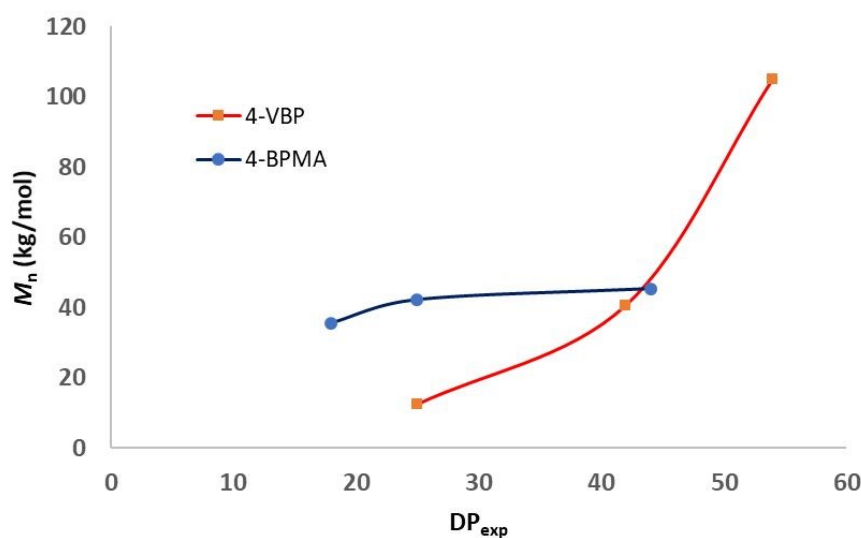**Figure 2.** Plot of DP_{exp} vs. M_n for 4-VBP and 4-BPMA (Table 1, entries 1–6).

To understand the details of the polymerization process, we monitored the trends in the molecular weight (M_n) and dispersity (Đ) as polymerization proceeded (0.10 g of 4-BPMA, [M]/[I] =50, eight 5 mm balls with 10 mL zirconia jar, 30 Hz, Figure 3). The monomer consumption was slow at the initial stage when alkyl lithium played an initiator role. After 10 min, no polymeric products were detected by ¹H NMR and SEC. After 20 min, the mixture contained a measurable amount of polymer (1% conv., M_n = 51.3 kg/mol, Đ = 1.10). Despite the small conversion, a high-molecular-weight polymer was obtained with narrow dispersity. The molecular weight continued to increase up to 30 min (6% conv., 61.3 kg/mol, Đ = 1.50). However, the increase in the molecular

weight did not follow this conversion. A sharp decrease in M_n was also observed, whereas the slope of the plot representing the increase in rate doubled after 40 min. The dispersity became broader. After 90 min, near-quantitative monomer consumption, despite continuous M_n reduction, was observed. The molecular weight reached 20.4 kg/mol at 120 min, which is one-third of the maximum M_n .

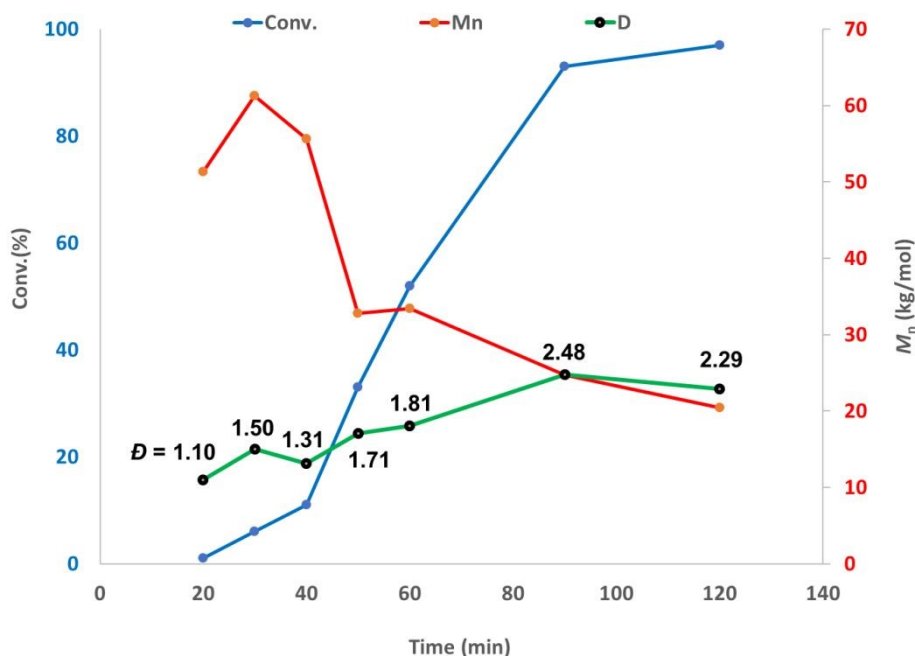


Figure 3. Plot of the polymerization time vs. conversion, number-average molecular weight, and dispersity. [4-BPMA (0.10 g), $[M]/[I] = 50$ in zirconia jar (10 mL) with eight zirconia balls (5 mm)].

Concurrent chain growth and degradation under ball-milling conditions have been reported in prior mechanochemical radical and ring-opening polymerizations. The overall observed trend of the anion-initiated polymerization was similar to that of the mechanochemical radical polymerization reported by Kuzuya.^[6h-j] The initial polymers were clearly obtained from *s*-BuLi initiation. A highly reactive secondary alkyl anion is buried in a 4-BPMA particle, and the high monomer concentration probably explains the high-molecular-weight product detected at 20 min. The narrow dispersity also supports anionic polymerization. The high-molecular-weight product, and thus the stiff polymer chain, subsequently underwent chain degradation during ball-milling.^[14] Fragmentation generates macroradicals and polymeric chains with a radical end, thereby promoting chain propagation. As more polymer chains are formed, chain degradation occurs more frequently; thus, the number of macroradicals increases. At this stage, radical propagation dominated anionic propagation, and overall monomer consumption was also accelerated.

To prove the involvement of this radical process, a selective anion-quenching experiment was performed (Figure 4). After 50 min of *s*-BuLi-initiated polymerization, a portion of a protic liquid, herein water (40 μ L), was added, which selectively quenched the alkyl anions. The mixture was placed in MM400 for further milling for 40 min. After 50 min of ball-milling with *s*-BuLi (mixture A), 41% of the intermediate was converted to the polymer ($M_n = 47.2$ kg/mol). Although water is expected to quench the alkyl anions, the polymerization process proceeded further, which may indicate macroradical-mediated radical propagation. Mechanical fracture resulted in a lower molecular weight product than that from mixture A (mixture B, $M_n = 12.7$ kg/mol).

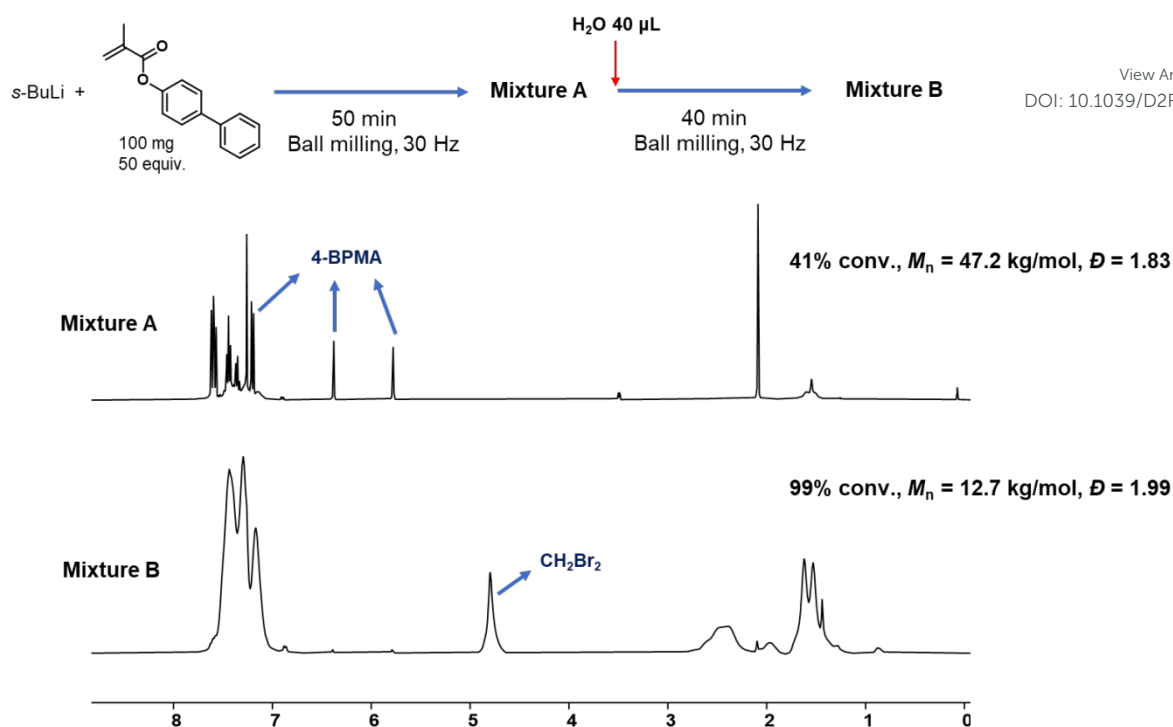


Figure 4. Procedure employed in anion quenching experiments and ^1H NMR spectra and M_n data for mixtures A and B.

Tacticity analysis also supported radical propagation (Figure 5). The ^{13}C NMR peak of the carbon in the α -position relative to the carbonyl group of three poly(4-BPMA) samples provided triad and dyad distributions: A) mechanochemical radical process (MM400, no initiator), B) mechanochemical anion-initiated polymerization after 60 min, and C) after 120 min.^[15] All three samples exhibited syndiotactic-rich structures with approximately 60% racemic(*r*) dyads and over 40% meso(*m*) dyads. Anion-initiated mechanochemical polymerization (Figure 5B and 5C) produced microstructures identical to those obtained via mechanochemical radical polymerization (Figure 5A). The anion-initiated polymerization of 4-BPMA followed a propagation mechanism similar to that of the radical pathway. The polymer structures obtained after 60 min (56% conv.), and 120 min (97% conv.) were almost identical. The same radical propagation process continued throughout the polymerization process.

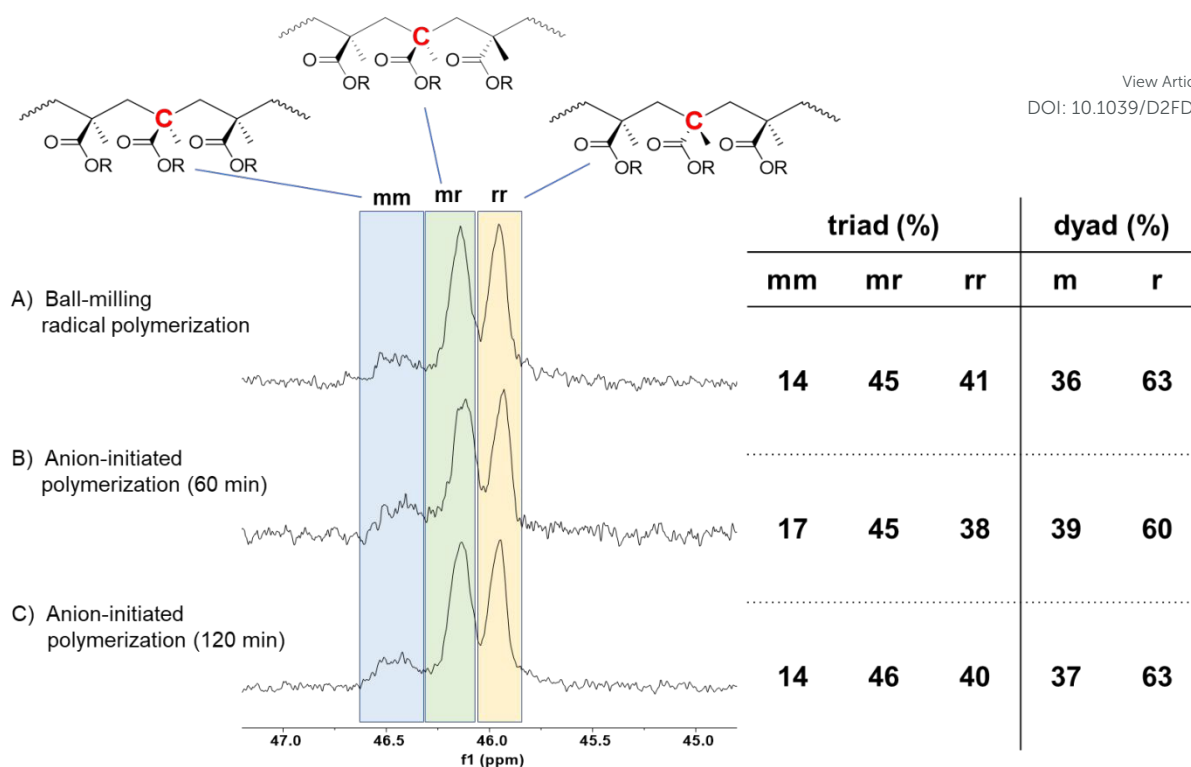


Figure 5. Comparison of stereoselectivity of different polymerization processes.

Conclusions

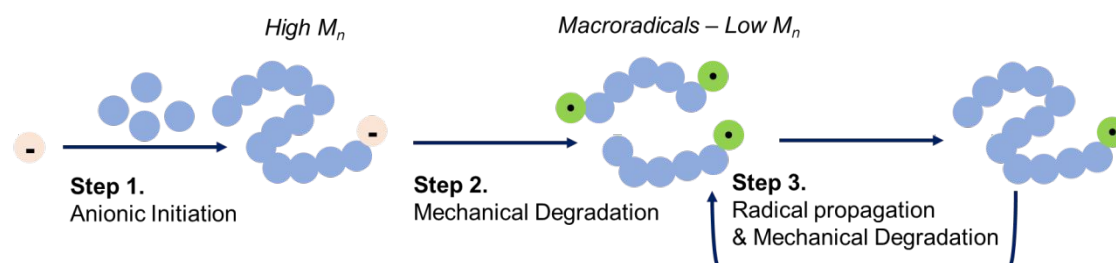


Figure 6. Schematic of anion-initiated mechanochemical polymerization: Anionic initiation and radical propagation.

Anionic polymerization, one of the most fundamental vinyl polymerizations, was performed under solid-state mechanochemical conditions. Polymerization of the vinyl monomer and alkyl anion initiator proceeded via anion initiation and radical propagation processes (Figure 6). The popular initiator *s*-BuLi successfully initiated the polymerization of styrenic and methacrylic monomers under conditions in which radical initiation was completely suppressed (step 1). Early anionic propagation produced a long polymer chain. Mechanical degradation of the resulting polymer chain generated macroradicals, a unique product of the mechanochemical process (step 2). Upon continuous macroradical feeding, radical chain propagation becomes dominant over anionic propagation. The concurrent radical propagation and chain degradation of macroradicals define the overall process (step 3). Time-resolved ^1H NMR/SEC and ^{13}C NMR microstructural analyses supported these results. This example indicates that the classical kinetics obtained in solution polymerization should be re-evaluated under solid-state ball-milling conditions. Further development for precise mechanochemical polymerization is in progress.

Experimental

View Article Online

DOI: 10.1039/D2FD00080F

General considerations

All the polymerization reactions were performed in a glove box to avoid contamination with air and moisture. *s*-BuLi and 4-VBP were used as-received. 4-BPMA was synthesised according to a previously reported method. A Retsch Mixer Mill MM 400 instrument was used for the ball-milling experiments.

Measurement

¹H and ¹³C NMR spectra were obtained using a Bruker Avance III HD Fourier-transform 400 MHz NMR spectrometer and referenced to the residual protonated solvent. SEC analyses with refractive index (RI) detection were used to determine the number-average molecular weight (M_n) and dispersity (\mathcal{D}). RI measurements were carried out using an instrument composed of a Waters 1515 isocratic pump, 2414 differential refractive index detector, and column-heating module with Shodex HK-403 and HK-404L columns placed in series. The columns were eluted with THF (preservative-free HPLC grade, Daejung Chemical Company) at 40 °C at 0.5 mL min⁻¹ and were calibrated using 16 monodisperse polystyrene standards (Alfa Aesar).

Representative anion-initiated polymerization of 4-BPMA (Table 2, entry 5)

4-BPMA (0.10 g, 50 equiv.) and *s*-BuLi (6 μ L, 1.4 M in cyclohexane, 1 equiv.) were added to a zirconia milling jar (10 mL), followed by the addition of zirconia balls (8 ea, 5 mm diameter). The tightly sealed vessel was placed in a vibrational ball-mill and subjected to 30 Hz vibration milling for an hour. The milling vial was then opened, and the internal standard CH₂Br₂ (20 μ L) was added. A portion of the resultant white powder was subjected to ¹H NMR spectroscopy and SEC measurements to determine its conversion and molecular weight. The average of the two experiments is reported. 50% conversion; SEC data (THF, PS standard): M_n = 42.2 kg mol⁻¹, \mathcal{D} = 1.81.

Conflicts of interest

There are no conflicts to declare

Acknowledgements

This work was supported by the Samsung Research Funding & Incubation Center of Samsung Electronics under project number SRFC-MA1902-05.

References

- [a] S. L. James and T. Friščić, *Mechanochemistry*, *Chem. Soc. Rev.*, **2013**, *42*, 7494–7496. [b] S. L. James, C. J. Adams, C. Bolm, D. Braga, P. Collier, T. Friščić, F. Grepioni, K. D. M. Harris, G. Hyett, W. Jones, A. Krebs, J. Mack, L. Maini, A. G. Orpen, I. P. Parkin, W. C. Shearouse, J. W. Steed and D. C. Waddell, *Mechanochemistry: opportunities for new and cleaner synthesis*, *Chem. Soc. Rev.*, **2012**, *41*, 413–447. [c] J.-L. Do and T. Friščić, *Mechanochemistry: A force of synthesis*, *ACS. Cent. Sci.*, **2017**, *3*, 13–19.
- [a] J. G. Hernández, *Mechanochemistry*, *Beilstein J. Org. Chem.*, **2017**, *13*, 2372–2373. [b] K. Kubota and H. Ito, *Mechanochemical cross-coupling reactions*, *Trends Chem.* **2020**, *2*, 1066–1081.
- [a] G.-W. Wang, *Mechanochemical organic synthesis*, *Chem. Soc. Rev.*, **2013**, *42*, 7668–7700. [b] A. Stolle, T. Szuppa, S. E. S. Leonhardt and B. Ondruschka, *Ball milling in organic synthesis: solutions and challenges*, *Chem. Soc. Rev.*, **2011**, *40*, 2317–2329. [c] E. Boldyreva, *Mechanochemistry of inorganic and organic systems: what is similar, what is different?*, *Chem. Soc. Rev.*, **2013**, *42*, 7719–7738. [d] N. R. Rightmire and T. P. Hanusa, *Advances in organometallic synthesis with mechanochemical methods*, *Dalton Trans.*, **2016**, *45*, 2352–2362. [e] D. Tan, L. Loots and T. Friščić, *Towards medicinal mechanochemistry: evolution of milling from pharmaceutical solid form screening to the synthesis of active pharmaceutical ingredients (APIs)*, *Chem. Commun.*, **2016**, *52*, 7760–7781. [f] D. Tan and F. García, *Main group mechanochemistry: from curiosity to established protocols*, *Chem. Soc. Rev.*, **2019**, *48*, 2274–2292.
- [a] P. A. May and J. S. Moore, *Polymer mechanochemistry: techniques to generate molecular force via elongational flows*, *Chem. Soc. Rev.*, **2013**, *42*, 7497–7506. [b] J. Li, C. Nagamani and J. S. Moore, *Polymer mechanochemistry: from destructive to productive*, *Acc. Chem. Res.*, **2015**, *48*, 2181–2190. [c] N. Willis-Fox, E. Rognin, T. A. Aljohani and R. Daly, *Polymer mechanochemistry: Manufacturing is now a force to be reckoned with*, *Chem*, **2018**, *4*, 2499–2537. [d] G. de Bo, *Polymer mechanochemistry and the emergence of the mechanophore concept*, *Macromolecules*, **2020**, *53*, 7615–7617.

- 5 A. Krusenbaum, S. Grätz, G. T. Tigineh, L. Borchardt and J. G. Kim, The mechanochemical synthesis of polymers, *Chem. Soc. Rev.* **2022**, *51*, 2873–2905.
- 6 [a] V. A. Kargin and N. A. Plate, Chemical grafting on crystal surfaces, *Vysokomol. Soed.* **1959**, *1*, 330. [b] K. A. Plate and V. A. Kargin, Mechanochemical reactions of polymerization and degradation at low temperatures, *J. Polym. Sci., Part C: Polym. Symp.* **1963**, *4*, 1027–1041. [c] V. A. Kargin, V. A. Kabanov and N. Rapaport-Molodtsova, The mechano-chemical initiation of polymerization of crystalline salts of acrylic acid, *Polym. Sci. USSR*, **1962**, *3*, 657–664. [d] V. A. Kargin and N. A. Plate, Polymerization and grafting processes on freshly formed surfaces, *J. Polym. Sci.*, **1961**, *52*, 155–158. [e] C. V. Oprea and M. Popa, Mechanochemically synthesized polymers with special properties, *Polym.-Plast. Technol. Eng.*, **1989**, *28*, 1025–1058. [f] C. Simionescu, C. Vasiliu Oprea and J. Nicoleanu, Mechanochemically initiated polymerizations—5. Polymerization by vibratory milling of acrylamide and methacrylamide, *Eur. Polym. J.*, **1983**, *19*, 525–528. [g] C. Simionescu, C. V. Oprea and C. Negulianu, Copolymerizations mechanochemically Initiated—I, *Eur. Polym. J.*, **1979**, *15*, 1037–1042. [h] M. Kuzuya, S. Kondo and A. Noguchi, A new development of mechanochemical solid-state polymerization of vinyl monomers: prodrug syntheses and its detailed mechanistic study, *Macromolecules*, **1991**, *24*, 4047–4053. [i] M. Kuzuya, S.-I. Kondo, A. Noguchi and N. Noda, Mechanistic study on mechanochemical polymerization of acrylamide, *J. Polym. Sci., Part A: Polym. Chem.*, **1991**, *29*, 489–494. [j] H. Y. Cho and C. W. Bielawski, Atom transfer radical polymerization in the solid-state, *Angew. Chem. Int. Ed.*, **2020**, *59*, 13929–13935.
- 7 [a] N. Ohn, J. Shin, S. S. Kim and J. G. Kim, Mechanochemical ring-opening polymerization of lactide: Liquid-assisted grinding for the green synthesis of poly(lactic acid) with high molecular weight, *ChemSusChem*, **2017**, *10*, 3529–3533. [b] G. S. Lee, B. R. Moon, H. Jeong, J. Shin and J. G. Kim, Mechanochemical synthesis of poly(lactic acid) block copolymers: overcoming the miscibility of the macroinitiator, monomer and catalyst under solvent-free conditions, *Polym. Chem.*, **2019**, *10*, 539–545. [c] S. Park and J. G. Kim, Mechanochemical synthesis of poly(trimethylene carbonate): an example of rate acceleration, *Beilstein J. Org. Chem.*, **2019**, *15*, 963–970. [d] T. F. Burton, J. Pinaud, N. Pétry, F. Lamaty and O. Giani, Simple and rapid mechanochemical synthesis of lactide and 3S-(isobutyl)morpholine-2,5-dione-based random copolymers using DBU and thiourea, *ACS Macro Lett.*, **2021**, *10*, 1454–1459.
- 8 G. S. Lee, H. W. Lee, H. S. Lee, T. Do, J.-L. Do, J. Lim, T. Friščić and J. G. Kim, Mechanochemical ring-opening metathesis polymerization: development, scope, and mechano-only copolymer synthesis, *ChemRxiv*, 10.33774/chemrxiv-2021-jh72b.
- 9 [a] S. Grätz, B. Wolfrum and L. Borchardt, Mechanochemical Suzuki polycondensation – from linear to hyperbranched polyphenylenes, *Green Chem.*, **2017**, *19*, 2973–2979. [b] S. Grätz and L. Borchardt, Mechanochemical polymerization – controlling a polycondensation reaction between a diamine and a dialdehyde in a ball mill, *RSC Adv.*, **2016**, *6*, 64799–64802. [c] C. G. Vogt, S. Grätz, S. Lukin, I. Halasz, M. Etter, J. D. Evans and L. Borchardt, Direct mechanocatalysis: palladium as milling media and catalyst in the mechanochemical Suzuki polymerization, *Angew. Chem. Int. Ed.*, **2019**, *58*, 18942–18947. [d] T. Rensch, S. Fabig, S. Grätz and L. Borchardt, Mechanochemically-assisted Synthesis of Polyimides, *ChemSusChem*, **2022**, *15*(1), e202101975. [e] J. B. Ravnsbæk and T. M. Swager, Mechanochemical synthesis of poly(phenylene vinylenes), *ACS Macro Lett.*, **2014**, *3*, 305–309. [f] C. Oh, E. H. Choi, E. J. Choi, T. Premkumar and C. Song, Facile solid-state mechanochemical synthesis of eco-friendly thermoplastic polyurethanes and copolymers using a biomass-derived furan diol, *ACS Sustainable Chem. Eng.*, **2020**, *8*, 4400–4406.
- 10 [a] H. Frey and T. Ishizone, Living anionic polymerization celebrates 60 years: Unique features and polymer architectures, *Macromol. Chem. Phys.*, **2017**, *218*, 1700217. [b] N. Hadjichristidis, M. Pitsikalis, S. Pispas and H. Iatrou, Polymers with complex architecture by living anionic polymerization, *Chem. Rev.*, **2001**, *101*, 3747–3792. [c] B.-G. Kang, Well-defined ABA triblock copolymers containing carbazole and ethynyl groups: living anionic polymerization, postpolymerization modification, and thermal cross-linking, *Macromol. Res.*, **2021**, *29*, 470–476.
- 11 [a] O. W. Webster, *J. Polym. Sci., Part A: Polym. Chem.*, **2000**, *38*, 2855–2860. [b] O. W. Webster, *Adv. Polym. Sci.*, **2004**, *167*, 1–34.
- 12 [a] H. Riaz, A. A. Shamsabadi, M. C. Grady, A. M. Rappe and M. Soroush, Experimental and theoretical study of the self-initiation reaction of methyl acrylate in free-radical polymerization, *Ind. Eng. Chem. Res.*, **2018**, *57*, 532–539. [b] K. S. Khuong, W. H. Jones, W. A. Pryor and K. N. Houk, The mechanism of the self-initiated thermal polymerization of styrene. theoretical solution of a classic problem, *J. Am. Chem. Soc.*, **2005**, *127*, 1265–1277.
- 13 R. B. Grubbs and R. H. Grubbs, 50th Anniversary perspective: Living polymerization-emphasizing the molecule in *Macromolecules*, *Macromolecules*, **2017**, *50*, 6979–6997.
- 14 [a] G. Janke and G. Schmidt-Naake, Synthesis of block and graft copolymers in a vibratory mill, *Chem. Eng. Technol.*, **2001**, *24*, 711–715. [b] G. I. Peterson, W. Ko, Y.-J. Hwang and T.-L. Choi, Mechanochemical degradation of amorphous polymers with Ball Mill grinding: Influence of the glass transition temperature, *Macromolecules*, **2020**, *53*, 7795–7802. [c] T. Q. Nguyen and H.-H. Kausch, Kinetics of polymer degradation in transient elongational flow, *Makromol. Chem.*, **1989**, *190*, 1389–1406. [d] T. Q. Nguyen and H.-H. Kausch, GPC Data Interpretation in mechanochemical polymer degradation, *Int. J. Polym. Anal. Charact.*, **1998**, *4*, 447–470.
- 15 [a] G. O. R. Alberda van Ekenstein and H. J. H. Altena and Y. Y. Tan, Polymerization of 4-biphenyl methacrylate; a kinetic study, *Eur. Polym. J.*, **1989**, *25*, 111–115. [b] Y. Suzuki, D. S. Cousins, Y. Shinagawa, R. T. Bell, A. Matsumoto and A. P. Stebner, Phase separation during bulk polymerization of methyl methacrylate, *Polym. J.*, **2019**, *51*, 423–431. [c] M. Miri, B. P. Pritchard and H. N. Cheng, A versatile approach of modelling and simulating the tacticity of polymers, *J. Mol. Model.*, **2011**, *17*, 1767–1780. [d] C. K. Ober, Polymer tacticity in simulated NMR spectra, *J. Chem. Edu.*, **1989**, *66*, 645–647.